

Zero phase delay in negative-refractive-index photonic crystal superlattices

S. Kocaman^{1*}, M. S. Aras¹, P. Hsieh¹, J. F. McMillan¹, C. G. Biris², N. C. Panoiu², M. B. Yu³, D. L. Kwong³, A. Stein⁴ and C. W. Wong^{1*}

We show that optical beams propagating in path-averaged zero-index photonic crystal superlattices can have zero phase delay. The nanofabricated superlattices consist of alternating stacks of negative index photonic crystals and positive index homogeneous dielectric media, where the phase differences corresponding to consecutive primary unit cells are measured with integrated Mach-Zehnder interferometers. These measurements demonstrate that at path-averaged zero-index frequencies the phase accumulation remains constant and equal to zero despite the increase in the physical path length. We further demonstrate experimentally that these superlattice zero- \bar{n} bandgaps remain invariant to geometrical changes of the photonic structure and have a center frequency which is deterministically tunable. The properties of the zero- \bar{n} gap frequencies, optical phase, and effective refractive indices are well described by detailed experimental measurements, rigorous theoretical analysis, and comprehensive numerical simulations.

An intense degree of interest in negative-index metamaterials (NIMs)^{1,2} has developed in recent years. Metal-based NIMs^{3–11} have been actively studied because of their unusual physical properties and their potential for use in many technological applications^{12–22}; however, they usually have the disadvantage of demonstrating large optical losses in their metallic components. As an alternative to metal-based NIMs, dielectric-based photonic crystals (PhCs) have been investigated and shown to emulate the basic physical properties of NIMs^{23–27}, while also having relatively small absorption losses at optical frequencies. Equally important, PhCs can be nanofabricated within current silicon foundries, suggesting significant potential for the development of future electronic–photonic integrated circuits.

One particular type of PhC can be obtained by cascading alternating layers of NIMs and positive-index materials (PIMs)^{28–32}. This photonic structure (Fig. 1) has unique optical properties, including new surface states and gap solitons^{33,34}, unusual transmission and emission properties^{35–39}, complete photonic bandgaps⁴⁰, and a phase-invariant field for cloaking applications⁴¹. Moreover, these binary photonic structures have an omnidirectional bandgap that is insensitive to wave polarization, incidence angle, structure periodicity and structural disorder^{42–44}. Such a gap exists because the path-averaged refractive index is equal to zero within a certain frequency band^{28–32,35}. At this frequency, the Bragg condition, $k\Lambda = (\bar{n}\omega/c)\Lambda = m\pi$, is satisfied for $m = 0$, irrespective of the period Λ of the superlattice (k and ω are the wave vector and frequency, respectively, and \bar{n} is the averaged refractive index). Because of this property this photonic bandgap is called zero- \bar{n} , or zero-order bandgap^{30,35}.

Near-zero-index materials have a series of exciting potential applications, such as beam self-collimation³⁵, extremely convergent lenses and spontaneous emission control³⁶, strong field enhancement³⁸ and cloaking devices⁴¹. The vanishingly small value of the refractive index of near-zero-index materials and their large phase velocity¹⁹ can reshape electromagnetic phase fronts emitted by

optical antennas³⁷ or, for highly directive antennas, transfer near-field phase information into the far-field. In the near-zero-index regime, the electromagnetic field has an unusual dual character; that is, it is static in the spatial domain (the phase difference between arbitrary spatial locations is equal to zero), while remaining dynamic in the time domain, thus allowing energy transport. Perhaps the most important application of near-zero-index materials is in optical links in lumped nanophotonic circuits⁴⁵. In particular, chip-scale optical interconnects or interferometers that can guide light over hundreds of wavelengths without introducing phase variations can be effectively used to reduce the unwanted effects of frequency dispersion. This remarkable property, which is also the main topic of our study, has other exciting technological applications in photon delay lines with zero phase difference, information-processing devices, and new optical phase control and measurement techniques.

In this Article, we demonstrate the zero phase delay at near-infrared wavelengths in chip-scale photonic superlattices that consist of alternating PhC-based NIM and homogeneous slab waveguide PIM layers. First, we observe the existence of the zero- \bar{n} gaps, a prerequisite for zero phase delays, and demonstrate the zero- \bar{n} gap invariance to structural changes and their deterministically tunable centre frequency. Next, by embedding the negative–positive index binary superlattices in integrated Mach–Zehnder interferometers (MZIs), we describe a series of measurements where the total phase accumulation in the superlattice is equal to zero, at the path-averaged zero-index frequencies. Furthermore, we present comparative phase delay studies across different superlattice configurations and negative-index unit cells, and detailed numerical simulations that prove that these zero- \bar{n} gaps are robust to effects induced by structural disorder.

Existence, invariance and tunability of zero- \bar{n} gap

First, we examine zero- \bar{n} superlattices and show experimentally that the zero- \bar{n} gap markedly differs from a regular Bragg gap.

¹Optical Nanostructures Laboratory, Center for Integrated Science and Engineering, Solid-State Science and Engineering, Mechanical Engineering, Columbia University, New York, New York 10027, USA, ²Photonics Group, Department of Electronic and Electrical Engineering, University College London, Torrington Place, London WC1E 7JE, UK, ³The Institute of Microelectronics, 11 Science Park Road, Singapore Science Park II, Singapore 117685, Singapore, ⁴Center for Functional Nanomaterials, Brookhaven National Laboratory, Upton, New York 11973, USA. *e-mail: sk2927@columbia.edu; cww2104@columbia.edu

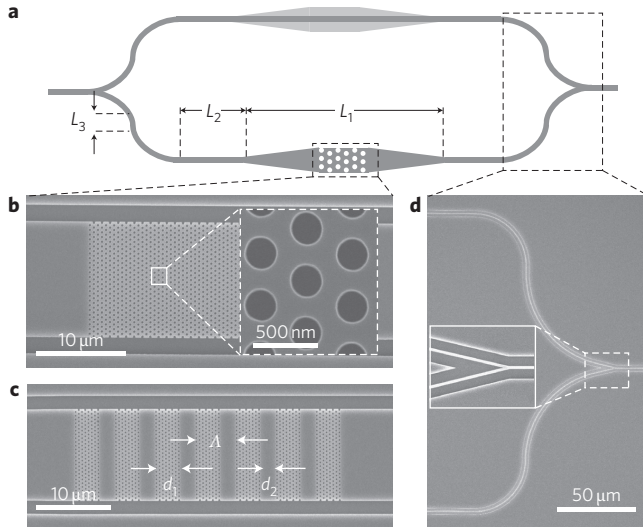


Figure 1 | Schematic of an MZI and scanning electron microscopy (SEM) images of the fabricated device. a, Schematic representation of the MZI ($L_1 \approx 850 \mu\text{m}$; $L_2 \approx 250 \mu\text{m}$; L_3 is initially zero and is incremented by additional SPs in the phase measurements). **b**, SEM image of a sample, showing the PhC layer only (period of hexagonal lattice, $a = 423 \text{ nm}$; ratio between hole radius and period, $r/a = 0.283$; ratio between thickness of wafer and period, $t/a = 0.756$). Inset: zoomed-in image. (For a schematic representation of the PhC and superlattice, see Supplementary Fig. S1.) **c**, SEM image of a fabricated superlattice with seven SPs. Each PhC layer contains seven unit cells of PhCs ($d_1 = 2.564 \mu\text{m}$, $d_2 = 2 \mu\text{m}$, $\Lambda = 4.564 \mu\text{m}$) with the same parameters as in **b**. **d**, SEM image of the Y-branch. Inset: zoomed-in image.

In particular, because this gap is formed when the spatially averaged index is zero, it is insensitive to superlattice period variations as long as the condition of zero average index is satisfied^{28–32,35}. This property also implies that the total phase accumulation upon beam propagation in the superlattice cancels at wavelengths corresponding to the zero- \bar{n} gap.

The existence of zero- \bar{n} bandgaps can be inferred from the Bloch–Floquet theorem, where for a one-dimensional (1D) binary periodic lattice the trace of the transfer matrix, T , of a primary unit cell can be expressed as^{28,30}

$$Tr[T(\omega)] = 2 \cos(\kappa\Lambda) = 2 \cos\left(\frac{\bar{n}\omega\Lambda}{c}\right) - \left(\frac{Z_1}{Z_2} + \frac{Z_2}{Z_1} - 2\right) \times \sin\left(\frac{n_1\omega d_1}{c}\right) \sin\left(\frac{n_2\omega d_2}{c}\right) \quad (1)$$

where $n_{1(2)}$ and $Z_{1(2)}$ are the refractive index and impedance of the first (second) layer, respectively, and κ is the Bloch wave vector of the electromagnetic mode. Equation (1) implies that if the spatially averaged refractive index is zero ($\bar{n} = 0$), all solutions for the wave vector are imaginary, which signifies the presence of a spectral bandgap^{28–31}.

The photonic structures examined for zero- \bar{n} gaps (Fig. 1) consist of dielectric PhC superlattices with alternating layers of negative-index PhC and positive-index homogeneous slabs³⁰. The PhC band structure is shown in Fig. 2a,b, with geometrical parameters from averaged fabricated samples (hole-to-lattice constant (r/a) ratio of 0.283 and $a \approx 423 \text{ nm}$). This two-dimensional (2D) hexagonal PhC has a negative index within the spectral band of 0.270–0.278, in normalized frequencies of $\omega a/2\pi c$, or wavelengths from 1,520 nm to 1,566 nm. The phase index of refraction is defined with respect to the wave vector in the first Brillouin zone, as

described in refs 27 and 46. Although alternative choices can be used, such as the wave vector of the plane wave with the largest amplitude in the Fourier series decomposition of the Bloch mode⁴⁷, our approach provides a convenient method with which to analyse the phase properties of the optical modes of the PhC. In our design, the longitudinal direction of the superlattice (z -axis) coincides with the Γ –M axis of the hexagonal PhC. The 1D binary superlattice and the hexagonal PhC have different symmetry properties and therefore different first Brillouin zones (Supplementary Fig. S1). Moreover, within our operating wavelength range (Fig. 2b) the PhC has two transverse-magnetic (TM)-like bands, one with a positive refractive index and the other with a negative refractive index, and an almost complete transverse-electric (TE)-like bandgap.

We fabricated a set of three devices of different periods Λ , with the negative-index PhC layer in the superlattice spanning 7, 9 and 11 unit cells along the z -axis, so that the thickness of this layer was $d_1 = 3.5\sqrt{3} a$ (2.564 μm), $d_1 = 4.5\sqrt{3} a$ (3.297 μm) and $d_1 = 5.5\sqrt{3} a$ (4.029 μm), respectively. Our experiments spanned 1,520 nm to 1,620 nm, with the negative refractive index band existing for wavelengths up to 1,570 nm. The effective refractive index of the PhC region was obtained from the band diagram (Fig. 2a,b, see Methods) and the PIM layer index computed from the asymmetric TM slab-waveguide mode effective index (for example, at 1,550 nm the mode index is 2.671). To locate the zero- \bar{n} frequency in the middle of our negative-index band, the length ratio between the PIM and PhC sections of the superlattice was set to 0.78. As such, the zero- \bar{n} gap should occur at 1,552.6 nm (see Supplementary Information). The corresponding PIM layer thickness was determined by requiring the average index to be zero [$\bar{n} = (n_1 d_1 + n_2 d_2)/\Lambda = 0$], while keeping the ratio d_2/d_1 unchanged for all three devices in the set. Here, n_1 and n_2 are the effective mode indices in the PhC and homogeneous layers, respectively, at the corresponding wavelengths. This leads to the following values for the superperiods (SPs): $\Lambda_{7\text{UC}} = 4.564 \mu\text{m}$, $\Lambda_{9\text{UC}} = 5.869 \mu\text{m}$ and $\Lambda_{11\text{UC}} = 7.173 \mu\text{m}$. Example transmission spectra for the fabricated samples are summarized in Fig. 2c, and show that the zero- \bar{n} gap is $\sim 1,557.8 \pm 1.5 \text{ nm}$, very close to the theoretically predicted values ($\Delta\lambda/\lambda < 0.5\%$) and numerically computed spectra. In the Supplementary Information, we further demonstrate the tunability of the zero- \bar{n} gap and provide near-field scanning optical microscope images to confirm transmission.

MZ interference with negative-refraction PhCs on both arms

We next examine PhC structures integrated with MZIs for phase-delay measurements. In most free-space interferometric applications, the phase difference leading to interference originates from the physical length difference between the two arms, but in integrated photonic circuits this delay can easily be modulated by the imbalance in the refractive indices of two arms (see Supplementary Information and ref. 48). As illustrated in Fig. 1a, the unbalanced interferometer is designed so that after splitting from the Y-branch (Fig. 1d); a single-mode input channel waveguide adiabatically tapers (over $\sim 400 \mu\text{m}$) to match the width of the superlattice structures. On the reference arm, there is either a slab (with or without PhC) that has the geometry required to match the index variations in the other arm and hence isolate the additional phase contribution of the PhC structures, or a channel waveguide leading to a large index difference and hence to distinctive Mach–Zehnder fringes.

For this purpose, we designed and fabricated 100 unit cells of PhC on one arm of the MZI and a geometrically identical homogeneous slab on the other arm (see Methods). In the transmission (Fig. 3b; red), the MZ interference spectra are slowly varying as expected, due to small imbalance in the MZI. However, there are two steep variations, the first at the end of the

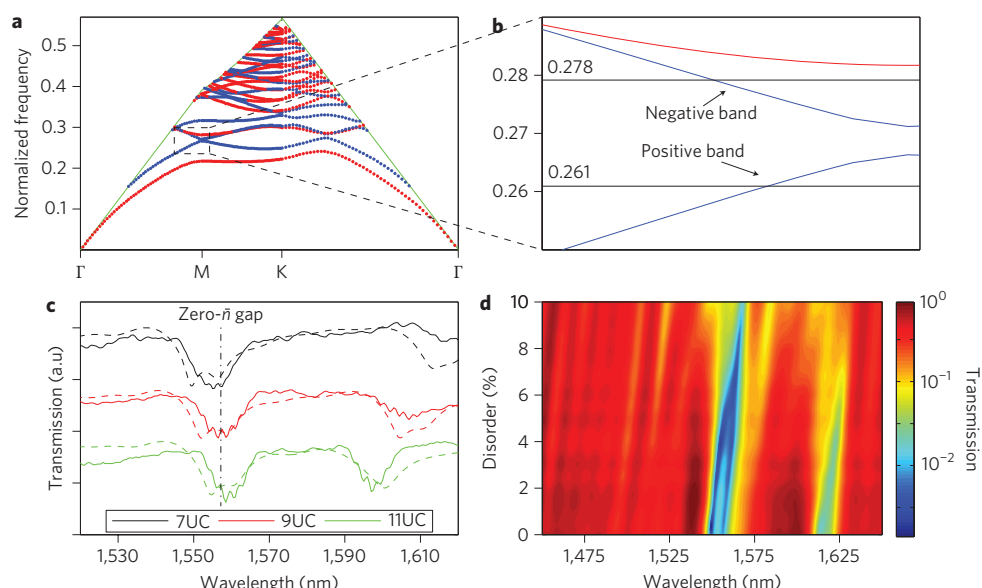


Figure 2 | Band diagram of the PhC, verification of period-invariant zero- \bar{n} bandgaps, and influence of structural variations on transmission spectra. **a**, Band diagram of the PhC with the parameters given in Fig. 1 (for a schematic of the Brillouin zones, see Supplementary Fig. S1). The TM-like and TE-like photonic bands are depicted in blue and red, respectively. The light cone is denoted by green lines. **b**, A zoomed-in representation of the spectral domain corresponding to the experimental region of interest. Experiments were performed in the spectral region delineated by two horizontal lines (normalized frequency, 0.278–0.261). **c**, Experimental verification of the zero- \bar{n} bandgap in superlattices with varying period ($\Lambda_{\text{black}} = 4.56 \mu\text{m}$, $\Lambda_{\text{red}} = 5.87 \mu\text{m}$ and $\Lambda_{\text{green}} = 7.17 \mu\text{m}$) and the same ratio $d_2/d_1 = 0.78$ (a.u., arbitrary units), and numerically simulated transmission spectra (dashed lines). **d**, Influence of lattice disorder (parameter σ) on transmission spectra. Colour bar: transmission scaling.

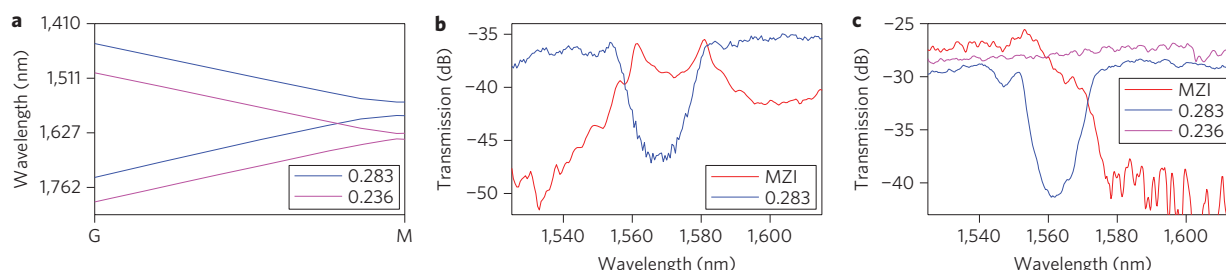


Figure 3 | MZ interferences with negative refraction PhCs. **a**, The band diagram shifts to lower frequency when the r/a ratio changes. Blue, original design; purple, design with $r/a = 0.236$. **b**, Red line: MZI transmission with 100 unit cells of PhC on one arm and a homogeneous slab waveguide on the other arm. Blue line: transmission spectrum for non-MZI PhC with 60 PhC unit cells. **c**, Red line: MZI transmission with 62 unit cells of PhC on one arm with $r/a = 0.283$ and 62 unit cells of PhC with $r/a = 0.236$ on the other arm; lattice period a is the same in both cases. Blue line: transmission spectrum for PhC superlattice with $r/a = 0.283$ and 80 unit cells of PhC. Purple line: transmission spectrum for PhC superlattice with $r/a = 0.236$ and 80 unit cells of PhC. Different index differences Δn from 1,525 nm to 1,550 nm and from 1,580 nm to 1,615 nm give different phase difference ϕ and different interference output.

first (negative-index) band and the second at the start of the second (positive-index) band. This is a clear indication of an abrupt refractive index change (Supplementary Fig. S2c), which is only possible when there is an abrupt switch between two photonic bands (a band-to-band transition). A non-MZI transmission spectrum of a similar structure is shown in Fig. 3b (blue) for reference.

To characterize this steep index change further, we placed on the two arms of the MZI PhC, sections of different radius r . We kept a unchanged to retain the same total physical length on both arms, for the same number of unit cells in the PhC sections. With this approach, the MZI sections that do not contain PhC regions are identical, so the two PhC sections are the only source for any measured phase difference. For example, we set r_2 to 5/6 of the original value of the radius r_1 ($r_2/a = 0.283 \times 5/6 = 0.236$). Figure 3a illustrates the difference between the band structures of the two PhC designs, namely, a frequency shift of the photonic bands. As

a result of this shifted band structure, the accumulated phase difference between the two arms is almost independent of wavelength, except for a steep variation that again corresponds to a steep refractive index change (moving from band to band). When we place a section of 62 PhC unit cells in both arms of the MZI, the transmission spectra have two spectral domains, 1,525–1,550 nm and 1,580–1,615 nm, where the interference transmission is rather constant (red curve in Fig. 3c) with ~ 14 dB transmission difference between the two domains (for high spatial resolution images, see Supplementary Fig. S6).

MZ phase delay measurements with photonic superlattices

Next, we prove that the total phase accumulation in the superlattices is zero. In these measurements we used a single-mode channel waveguide for the MZI reference arm. Owing to the large imbalance between the tapering slab and the channel waveguide, a series of high-visibility interference fringes can be observed at the output

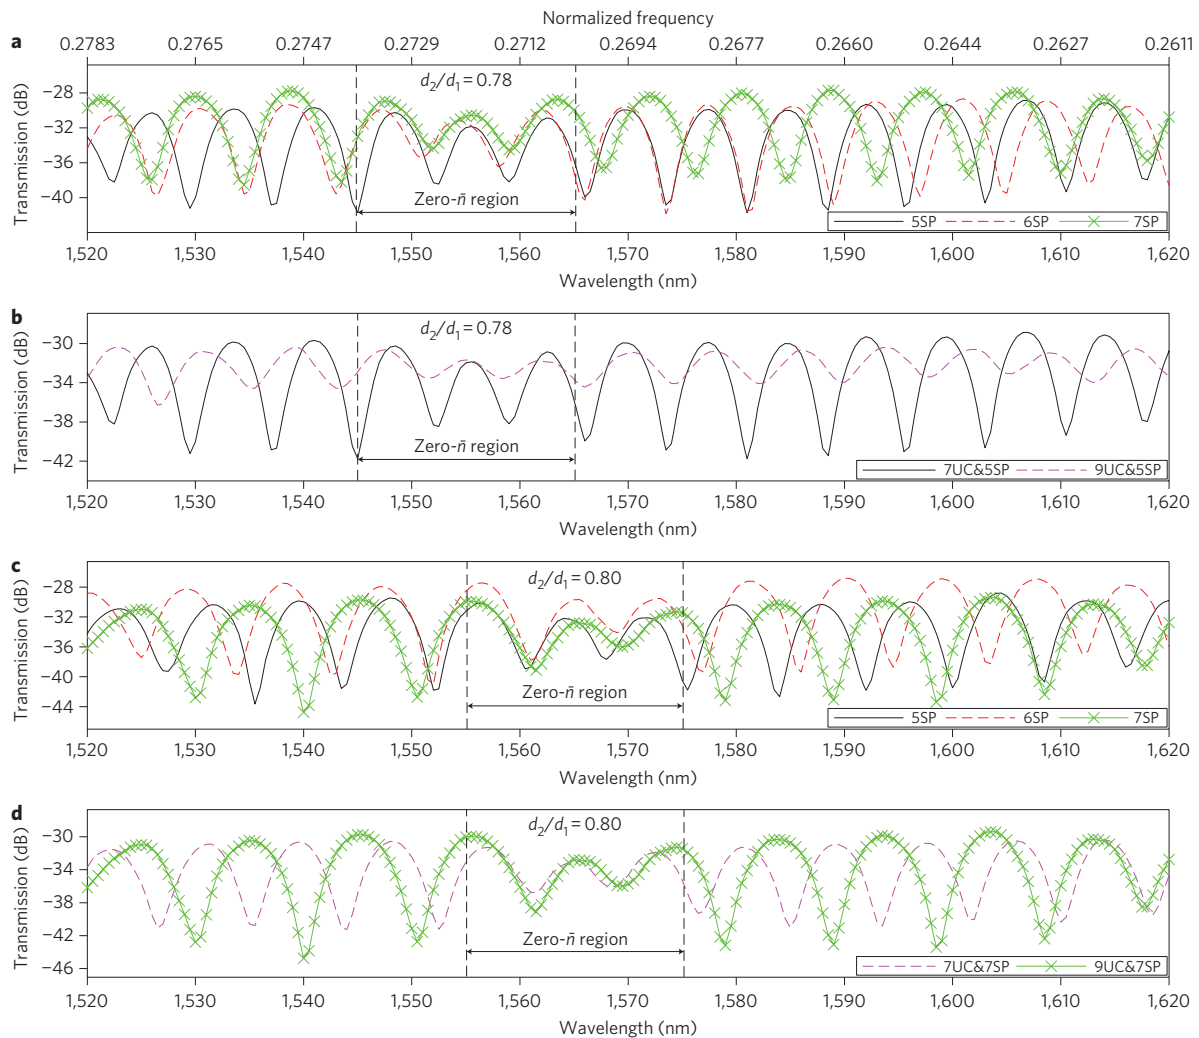


Figure 4 | Phase measurements. **a**, Output of the MZI with increasing number of SPs (5, 6 and 7) on one arm and single-mode channel waveguides on the other. Each PhC layer contains seven unit cells ($d_1 = 2.564 \mu\text{m}$, $d_2 = 2$, $d_2/d_1 = 0.78$ and $\Lambda = 4.564 \mu\text{m}$). **b**, As in **a**, with increasing number of unit cells in each SP (7UC, $\Lambda = 4.564 \mu\text{m}$; 9UC, $\Lambda = 5.869 \mu\text{m}$); each device has five SPs. **c**, As in **a**, but for $d_2/d_1 = 0.8$ and nine unit cells in each PhC layer ($d_1 = 3.297 \mu\text{m}$, $d_2 = 2.572$, $d_2/d_1 = 0.78$, $\Lambda = 5.869 \mu\text{m}$). **d**, As in **b**, with $d_2/d_1 = 0.8$ (7UC, $\Lambda = 4.616 \mu\text{m}$; 9UC, $\Lambda = 5.935 \mu\text{m}$); each device has seven SPs.

and used to determine the phase delay by analysing the fringe spectral locations and peak-to-peak free spectral range (FSR). We designed the taper length to have a large number of fringes within the measurement window. With this approach we avoid the uncertainty of transmission and coupling losses (and the resulting normalization by the individual device transmissions) when determining the phase differences between devices. We performed phase measurements for four different sets of devices: (i) $d_2/d_1 = 0.78$ and seven unit cells in the PhC layer, with increasing number of SPs (5, 6 and 7); (ii) $d_2/d_1 = 0.78$ and five SPs with different unit cells in the PhC layers (7 and 9); (iii) $d_2/d_1 = 0.80$ and nine unit cells in the PhC layer with increasing number of SPs (5, 6 and 7); and (iv) $d_2/d_1 = 0.80$ and seven SPs with different unit cells in the PhC layers (7 and 9). When we designed these devices, we modified the MZI so that when we added a SP to the superlattice the length of the adiabatic transition arms was increased by $\Lambda/2$, making the horizontal single-mode channel waveguides shorter (from L_2 to $L_2 - \Lambda/2$), at both the input and output sides of the device arm in Fig. 1a (for a schematic illustration, see Supplementary Fig.S3). This change is compensated by adding the same length to the vertical part (from L_3 to $L_3 + \Lambda/2$ on both sides in Fig. 1a). As a result, the only phase difference between devices is due to the additional SPs. At each wavelength, the

phase difference between the waves propagating in the two arms of the MZI is given by (see Supplementary Information)

$$\cos[\phi] = \cos\left[\frac{2\pi}{\lambda} \left((n_{\text{slab}} - n_{\text{wg}})L_{\text{slab}} + n_{\text{sl}}L_{\text{sl}} \right)\right] \quad (2)$$

where n_{slab} , n_{wg} and n_{sl} are the refractive indices of the tapering slab, the channel waveguide and the superlattice, respectively. These have different frequency dispersions, and therefore different functional dependence on the probed wavelength. L_{sl} and L_{slab} are the physical lengths of the superlattice and the tapering slab (total $\sim 850 \mu\text{m}$). Figure 4a shows the interference pattern for $d_2/d_1 = 0.78$ with seven unit cells in the PhC layer. As shown, outside the zero- \bar{n} spectral region the fringes differ from each other both in wavelength and FSR, but overlap very well within the zero- \bar{n} spectral domain, indicating that the additional phase contribution from the $n_{\text{sl}}L_{\text{sl}}$ term in equation (2) is zero.

To further illustrate the phase evolution, we show in Fig. 5a the FSR values for each of the devices examined — specifically, we calculate the spectral spacing between the transmission minima and plot the spectral spacing versus centre wavelength between the two

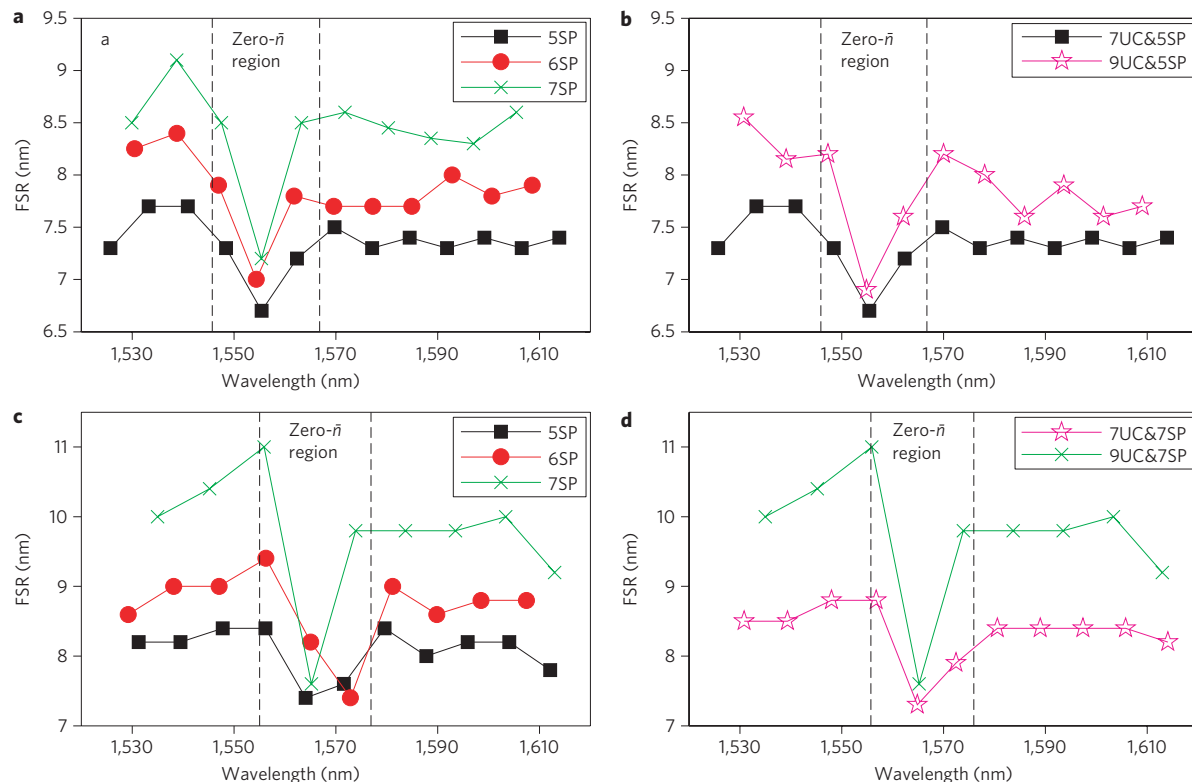


Figure 5 | FSR wavelength dependence corresponding to superlattices in Fig. 4. a–d, FSR spectral spacing between the transmission minima versus centre wavelength between the two neighbouring minima, extracted from the data in Fig. 4a–d. At the zero- \bar{n} bandgap wavelength, the FSR does not change between devices when the physical length of the MZI arm increases, which proves the zero phase contribution from the added SPs.

neighbouring minima. As noted above, in general there is an inherent FSR due to the MZI imbalance, and after adding each SP the FSR increases, so the imbalance decreases. However, in the zero- \bar{n} spectral domain the FSR corresponding to each of the devices approaches the same value, indicating that the corresponding phase difference remains constant. This is a surprising conclusion, because the physical path is certainly not the same in all cases. This apparent paradox has a simple explanation: although the physical path difference varies among the three cases the corresponding optical path difference is the same as the spatially averaged refractive index of the three superlattices vanishes. In other words, within the zero- \bar{n} spectral region the photonic superlattice emulates the properties of a zero phase delay line.

The output corresponding to the structures with $d_2/d_1 = 0.78$ and five SPs with different unit cells (7 and 9) in the PhC layer is shown in Fig. 4b, and the FSR values are plotted in Fig. 5b. Here, the device with seven unit cells is the same as the one corresponding to the results in Fig. 4a. Remarkably, although the additional length is different in this case (instead of a length difference of $2 \times \Lambda_{7UC}$, we have now added a length of $5 \times (\Lambda_{9UC} - \Lambda_{7UC})$), we again obtain a good overlap in the interference pattern and a match in the FSR value. Therefore, the phase difference is independent of the length of the superlattice (see also equation 2); this further proves that we indeed observe a zero phase difference and not a multiple of 2π . In other words, if $\bar{n} \times \Lambda_{7UC}$ ($\bar{n} \times 4.56 \mu\text{m}$) and $\bar{n} \times \Lambda_{9UC}$ ($\bar{n} \times 5.87 \mu\text{m}$) are multiples of $\lambda/2$ at $\lambda = 1,557.8 \text{ nm}$, the only possible solution is that the multiple is equal to zero. With this, we also prove a fundamental difference between a Bragg gap and the zero- \bar{n} gap; the former scales with the lattice period Λ and forms at multiples of 2π , whereas the latter is independent of Λ and occurs at a constant wavelength as long as the property of path-averaged zero index is preserved.

Finally, Fig. 4c,d and Fig. 5c,d show the interference patterns for the case of $d_2/d_1 = 0.80$ and nine unit cells in the PhC layer with increasing number of SPs (5, 6 and 7) and with seven SPs with changing number of unit cells in the PhC layer (7 and 9), respectively. Again, both the FSR (Fig. 5c,d) and absolute wavelength values (Fig. 4c,d) overlap in the zero- \bar{n} spectral domain, proving the zero phase variation across the superlattices.

Robustness against structural disorder

One of the main properties of zero- \bar{n} bandgaps is their remarkable robustness against effects induced by structural disorder. To study this property, we considered the optical transmission in randomly perturbed photonic superlattices. Specifically we considered superlattices for which the PIM lengths were randomly distributed within the domain ($d_2 - \Delta d_2/2$, $d_2 + \Delta d_2/2$), amounting to a random variation of SP Λ . The degree of structural disorder is quantified by the parameter $\sigma = \Delta d_2/d_2$. The main results of our computational investigation are presented in Fig. 2d. It can be clearly seen that the zero- \bar{n} bandgap is preserved, even when the disorder parameter is as large as $\sigma = 10\%$, that is, a value much larger than arising from our fabrication processes. Note that the amplitude oscillations in the transmission spectra represent Fabry–Perot resonances in the superlattice. In addition, our numerical simulations show that the structural disorder associated with a random perturbation of the hole radii or their location has a comparable or smaller influence on the existence of zero- \bar{n} bandgaps (Supplementary Fig. S7a,b).

Conclusion

We have demonstrated, for the first time, zero phase delay in negative–positive-index superlattices, in addition to observations of deterministic zero- \bar{n} gaps that remain invariant to geometric changes. Through stable chip-scale interferometric measurements,

binary superlattices of varying lengths are shown unequivocally to enable rigorous control of the optical phase. Devices with different SPs, unit cells and negative–positive length ratios have all demonstrated the presence of the zero phase delay. Engineered control of the phase delay in these near-zero refractive index superlattices can be implemented in chip-scale transmission lines and interferometers with deterministic phase array and dispersion control, and has significant technological potential in phase-insensitive image processing, phase-invariant fields for electromagnetic cloaking, lumped elements in optoelectronics, information processing, and engineering of radiation wavefronts to pre-designed shapes.

Methods

Numerical simulations. The band diagram in Fig. 2a was calculated using RSoft's BandsOLVE, a commercially available software that implements a numerical method based on the plane wave expansion of the electromagnetic field. Three-dimensional simulations were performed to calculate 30 bands. In all these numerical simulations, a convergence tolerance of 1×10^{-8} was used. The photonic bands were divided into TM-like and TE-like, according to their parity symmetry. The path-averaged index of the superlattice was calculated using the negative effective index of the second TM-like band and the effective modal index of the homogeneous asymmetric slab waveguide.

The effective refractive indices corresponding to the TM-like bands (Fig. 2b) were determined from the relation $k = \omega n/c$ (with k in the first Brillouin zone) (see Supplementary Information). Note that, for the second band, the effective index of refraction is negative because k decreases with ω (ref. 23).

The transmission spectra were determined using MIT's MEEP⁴⁹, a freely available code based on the finite-difference time-domain (FDTD) method. In all numerical simulations we used a uniform computational grid of 40 grid points per micrometre. This ensured that a widely used rule-of-thumb for setting the size of the computational grid in FDTD simulations was satisfied, namely, that the smallest characteristic length of the system (in our case, the diameter of the holes) contained at least 10 grid points. The transmission spectra corresponding to a specific geometry of the photonic superlattice were determined by normalizing the transmission spectrum of the photonic superlattice to the transmission spectrum of the homogeneous structure that was obtained by replacing the PhC regions with homogeneous slabs. In all our FDTD-based numerical simulations we used a pulsed excitation source with a central wavelength of $\lambda_0 = 1,550$ nm and spectral full-width at half-maximum of 90 nm. A typical simulation run on 64 Intel®Xeon processors was performed in ~ 7 h.

Sample nanofabrication. The PhC structures shown in Fig. 1 were fabricated as a hexagonal lattice of air holes arranged on a silicon on insulator (SOI) wafer with a 320 nm-thick silicon slab ($n_{\text{Si}} = 3.48$) on top of a 2- μm -thick layer of buried oxide ($n_{\text{SiO}_2} = 1.46$), either with electron-beam or deep-UV lithography. For electron-beam lithography, ZEP520A (100%) positive tone electron-beam resist was spin-coated at 4,000 r.p.m. to a thickness of 370 nm, and baked at 180 °C for 3 min. A JEOL JBX6300FS electron-beam lithography system was used to expose the pattern, followed by development in amyl acetate for 90 s, and rinsing with isopropyl alcohol (IPA) for 45 s to completely remove the developer (amyl acetate) residue.

For pattern transferring into silicon, an Oxford instruments Plasmalab 100 was used to perform cryogenic etching of the silicon⁵⁰ using an inductively coupled plasma reactive ion etcher (ICP-RIE). First, we applied 10 min O_2 cleaning at -100 °C in the chamber, followed by cryogenic etching at -100 °C using a mixture of SF_6 (40 s.c.c.m) and O_2 (18 s.c.c.m.) at 15 W radiofrequency (rf) power, 800 W ICP power and 12 mtorr pressure for a total of 18 s. Subsequently, the wafer was placed in 1165 resist remover for ~ 4 h to completely remove the remainder of the resist. The chip was cleaved and mounted on the sample holder for measurements.

Experiments. An in-line fibre polarizer with a polarization controller was used to couple TE light from an amplified spontaneous emissions source (ranging from 1,520 nm to 1,620 nm) into the waveguide via a tapered lensed fibre. A second tapered lensed fibre collected the transmission from the waveguide output, and the signal was sent to an optical spectrum analyser (OSA).

It should be noted that in all our plots of experimental data we used raw data, so there was no data post-processing, except for intensity rescaling. Measurements were taken three times with 500 pm resolution for Figs 2c and 3b,c, 100 pm and 500 pm resolutions for Fig. 4a, and 200 pm and 500 pm resolutions for Fig. 4b–d. There is $\sim 0.5\%$ deviation between Fig. 3b and Fig. 3c in terms of the centre frequency of the bandgap region, because of fabrication differences between the samples. In Figs 2c, 4 and 5, the r/a ratio was $< 5\%$ smaller than in Fig. 3b, resulting in a shift of the band structure to lower frequencies (but in Fig. 3c was $< 5\%$ larger than in Fig. 3b, leading to a shift of the band structure to higher frequencies), consequently causing a shift of the zero- n bandgap.

For the three devices in Fig. 2c, we designed seven SPs for the devices with seven unit cells of PhC, and five SPs for those with nine and eleven unit cells of PhC, to ensure a sufficient signal-to-noise ratio for the transmission measurements.

Received 28 November 2010; accepted 26 May 2011;
published online 10 July 2011

References

- Veselago, V. G. The electrodynamics of substances with simultaneously negative values of ϵ and μ . *Usp. Fiz. Nauk* **92**, 517–526 (1964) [*Sov. Phys. Usp.* **10**, 509–514 (1968)].
- Pendry, J. B. Time reversal and negative refraction. *Science* **322**, 71–73 (2008).
- Shelby, R. A., Smith, D. R. & Schultz, S. Experimental verification of a negative index of refraction. *Science* **292**, 77–79 (2001).
- Valentine, J. *et al.* Three-dimensional optical metamaterial with a negative refractive index. *Nature* **455**, 376–379 (2008).
- Li, N. *et al.* Three-dimensional photonic metamaterials at optical frequencies. *Nat. Mater.* **7**, 31–37 (2008).
- Gramotnev, D. K. & Bozhevolnyi, S. I. Plasmonics beyond the diffraction limit. *Nature Photon.* **4**, 83–91 (2010).
- Shalaev, V. M. Optical negative-index metamaterials. *Nature Photon.* **1**, 41–48 (2007).
- Kundtz, N. & Smith, D. R. Extreme-angle broadband metamaterial lens. *Nat. Mater.* **9**, 129–132 (2010).
- Panoiu, N. C. & Osgood, R. M. Influence of the dispersive properties of metals on the transmission characteristics of left-handed materials. *Phys. Rev. E* **68**, 016611 (2003).
- Zhang, S. *et al.* Demonstration of near-infrared negative-index metamaterials. *Phys. Rev. Lett.* **95**, 137404 (2005).
- Liu, R. *et al.* Experimental demonstration of electromagnetic tunneling through an epsilon-near-zero metamaterial at microwave frequencies. *Phys. Rev. Lett.* **100**, 023903 (2008).
- Tsakmakidis, K. L., Boardman, A. D. & Hess, O. 'Trapped rainbow' storage of light in metamaterials. *Nature* **450**, 397–401 (2007).
- Yao, J. *et al.* Optical negative refraction in bulk metamaterials of nanowires. *Science* **321**, 930 (2008).
- Xi, S. *et al.* Experimental verification of reversed Cherenkov Radiation in left-handed metamaterial. *Phys. Rev. Lett.* **103**, 194801 (2009).
- Hoffman, A. J. *et al.* Negative refraction in semiconductor metamaterials. *Nat. Mater.* **6**, 946–950 (2007).
- Grigorenko, A. N. *et al.* Nanofabricated media with negative permeability at visible frequencies. *Nature* **438**, 335–338 (2005).
- Dolling, G., Enkrich, C., Wegener, M., Soukoulis, C. M. & Linden, S. Simultaneous negative phase and group velocity of light in a metamaterials. *Science* **312**, 892–894 (2006).
- Pollard, R. J. *et al.* Optical nonlocalities and additional waves in epsilon-near-zero metamaterials. *Phys. Rev. Lett.* **102**, 127405 (2009).
- Ye, D., Qiao, S., Huangfu, J. & Ran, L. Experimental characterization of the dispersive behavior in a uniaxial metamaterial around plasma frequency. *Opt. Express* **18**, 22631–22636 (2010).
- Jin, Y., Zhang, P. & He, S. Squeezing electromagnetic energy with a dielectric split ring inside a permeability-near-zero metamaterial. *Phys. Rev. B* **81**, 085117 (2010).
- Hsueh, W. J., Chen, C. T. & Chen, C. H. Omnidirectional band gap in Fibonacci photonic crystals with metamaterials using a band-edge formalism. *Phys. Rev. A* **78**, 013836 (2008).
- Xu, J.-P., Yang, Y.-P., Chen, H. & Zhu, S.-Y. Spontaneous decay process of a two-level atom embedded in a one-dimensional structure containing left-handed material. *Phys. Rev. A* **76**, 063813 (2007).
- Chatterjee, R. *et al.* Achieving subdiffraction imaging through bound surface states in negative-refraction photonic crystals in the near-infrared range. *Phys. Rev. Lett.* **100**, 187401 (2008).
- Decoopman, T., Tayeb, G., Enoch, S., Maystre, D. & Gralak, B. Photonic crystal lens: from negative refraction and negative index to negative permittivity and permeability. *Phys. Rev. Lett.* **97**, 073905 (2006).
- Lu, Z. *et al.* Three-dimensional subwavelength imaging by a photonic-crystal flat lens using negative refraction at microwave frequencies. *Phys. Rev. Lett.* **95**, 153901 (2005).
- Parimi, P. V., Lu, W. T., Vodo, P. & Sridhar, S. Photonic crystals: imaging by flat lens using negative refraction. *Nature* **426**, 404 (2003).
- Notomi, M. Theory of light propagation in strongly modulated photonic crystals: Refractionlike behavior in the vicinity of the photonic band gap. *Phys. Rev. B* **62**, 010696 (2000).
- Li, J., Zhou, L., Chan, C. T. & Sheng, P. Photonic band gap from a stack of positive and negative index materials. *Phys. Rev. Lett.* **90**, 083901 (2003).
- Panoiu, N. C., Osgood, R. M., Zhang, S. & Brueck, S. R. J. Zero- n bandgap in photonic crystal superlattices. *J. Opt. Soc. Am. B* **23**, 506–513 (2006).
- Kocaman, S. *et al.* Observations of zero-order bandgaps in negative-index photonic crystal superlattices at the near-infrared. *Phys. Rev. Lett.* **102**, 203905 (2009).
- Yuan, Y. *et al.* Experimental verification of zero order bandgap in a layered stack of left-handed and right-handed materials. *Opt. Express* **14**, 2220–2227 (2006).

32. Zhang, L., Zhang, Y., He, L., Li, H. & Chen, H. Experimental investigation on zero- n_{eff} gaps of photonic crystals containing single-negative materials. *Eur. Phys. J. B* **62**, 1–6 (2008).
33. Hegde, R. S. & Winful, H. G. Zero- n gap soliton. *Opt. Lett.* **30**, 1852–1854 (2005).
34. Namdar, A., Shadrivov, I. V. & Kivshar, Y. S. Excitation of backward Tamm states at an interface between a periodic photonic crystal and a left-handed metamaterial. *Phys. Rev. A* **75**, 053812 (2007).
35. Mocella, V. *et al.* Self-collimation of light over millimeter-scale distance in a quasi-zero-average-index metamaterial. *Phys. Rev. Lett.* **102**, 133902 (2009).
36. Enoch, S., Tayeb, G., Sabouroux, P., Guérin, N. & Vincent, P. A metamaterial for directive emission. *Phys. Rev. Lett.* **89**, 213902 (2002).
37. Ziolkowski, R. W. Propagation in and scattering from a matched metamaterial having a zero index of refraction. *Phys. Rev. E* **70**, 046608 (2004).
38. Litchinitser, N. M., Maimistov, A. I., Gabitov, I. R., Sagdeev, R. Z. & Shalaev, V. M. Metamaterials: electromagnetic enhancement at zero-index transition. *Opt. Lett.* **33**, 2350–2352 (2008).
39. Wang, L.-G., Li, G.-X. & Zhu, S.-Y. Thermal emission from layered structures containing a negative-zero-positive index metamaterial. *Phys. Rev. B* **81**, 073105 (2010).
40. Shadrivov, I. V., Sukhorukov, A. A. & Kivshar, Y. S. Complete band gaps in one-dimensional left-handed periodic structures. *Phys. Rev. Lett.* **95**, 193903 (2005).
41. Hao, J., Yan, W. & Qiu, M. Super-reflection and cloaking based on zero index metamaterial. *Appl. Phys. Lett.* **96**, 101109 (2010).
42. Jiang, H., Chen, H., Li, H., Zhang, Y. & Zhu, S. Omnidirectional gap and defect mode of one-dimensional photonic crystals containing negative-index materials. *Appl. Phys. Lett.* **83**, 5386 (2003).
43. Bria, D. *et al.* Band structure and omnidirectional photonic band gap in lamellar structures with left-handed materials. *Phys. Rev. E* **69**, 066613 (2004).
44. Davoyan, A. R., Shadrivov, I. V., Sukhorukov, A. A. & Kivshar, Y. S. Bloch oscillations in chirped layered structures with metamaterials. *Opt. Express* **16**, 3299–3304 (2008).
45. Engheta, N. Circuits with light at nanoscales: optical nanocircuits inspired by metamaterials. *Science* **317**, 1698–1702 (2007).
46. Foteinopoulou, S. & Soukoulis, C. M. Electromagnetic wave propagation in two-dimensional photonic crystals: a study of anomalous refractive effects. *Phys. Rev. B* **72**, 165112 (2005).
47. Yariv, A. & Yeh, P. *Optical Waves in Crystals: Propagation and Control of Laser Radiation* (Wiley, 1984).
48. Vlasov, Y. A., O'Boyle, M., Hamann, H. F. & McNab, S. J. Active control of slow light on a chip with photonic crystal waveguides. *Nature* **438**, 65–69 (2005).
49. Oskooi, A. F. *et al.* MEEP: a flexible free-software package for electromagnetic simulations by the FDTD method. *Comp. Phys. Commun.* **181**, 687–702 (2010).
50. Henry, M. D., Welch, C. & Scherer, A. Techniques of cryogenic reactive ion etching in silicon for fabrication of sensors. *J. Vac. Sci. Technol. A* **27**, 1211–1216 (2009).

Acknowledgements

The authors thank R. Chatterjee for helpful discussions and Ayse Selin Kocaman for the preparation of figures. The authors also acknowledge funding support from a NSF CAREER Award (0747787), NSF ECCS (1102257), DARPA InPho and the EPSRC (EP/G030502/1). Electron-beam nanopatterning was carried out at the Center for Functional Nanomaterials, Brookhaven National Laboratory, which is supported by the US Department of Energy, Office of Basic Energy Sciences (contract no. DE-AC02-98CH10886). The authors acknowledge the use of the UCL Legion High Performance Computing Facility and associated support services in the completion of this work.

Author contributions

S.K. performed the experiments. M.S.A., M.B.Y., D.L.K. and A.S. nanofabricated the samples. P.H. performed near-field measurements. S.K., J.F.M., C.G.B. and N.C.P. designed and performed the numerical simulations. S.K., N.C.P. and C.W.W. prepared the manuscript.

Additional information

The authors declare no competing financial interests. Supplementary information accompanies this paper at www.nature.com/naturephotonics. Reprints and permission information is available online at <http://www.nature.com/reprints>. Correspondence and requests for materials should be addressed to S.K. and C.W.W.

Supplementary Information

I. Schematic representation of the zero- \bar{n} superlattices

Schematic representation of a superlattice with 3 superperiods is shown in Fig. S1. The superlattice consists of alternating layers of hexagonal PhCs and homogeneous slabs. Note that the hexagonal PhC and the photonic superlattice have different symmetry properties, and therefore they also have different first Brillouin zones.

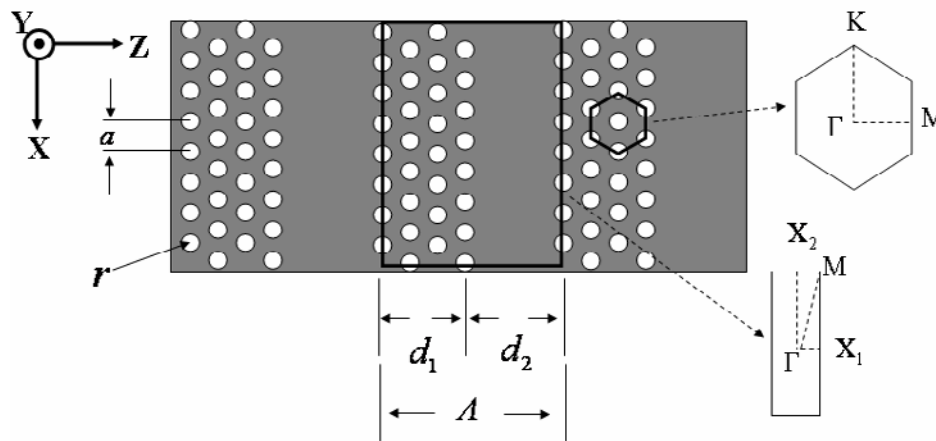


Figure S1 | Schematic representation of the photonic superlattice. There are two Brillouin zones defined as follows: one for the hexagonal photonic crystal lattice and one for the photonic superlattice. a is the lattice period and r is the radius of the holes forming the hexagonal lattice. d_1 is the length of the PhC layer and d_2 is the length of the PIM region. $d_1 + d_2 = A$ is equal to the superperiod (SP) of the photonic superlattice.

II. Effective indices from band diagram

The effective refractive indices corresponding to the TM-like bands (Fig. S2b) are determined from the relation $k=\omega n/c$ (with k in the first Brillouin zone) and plotted in Fig. S2c. Note that for the second band the effective index of refraction is negative since k decreases with ω [23].

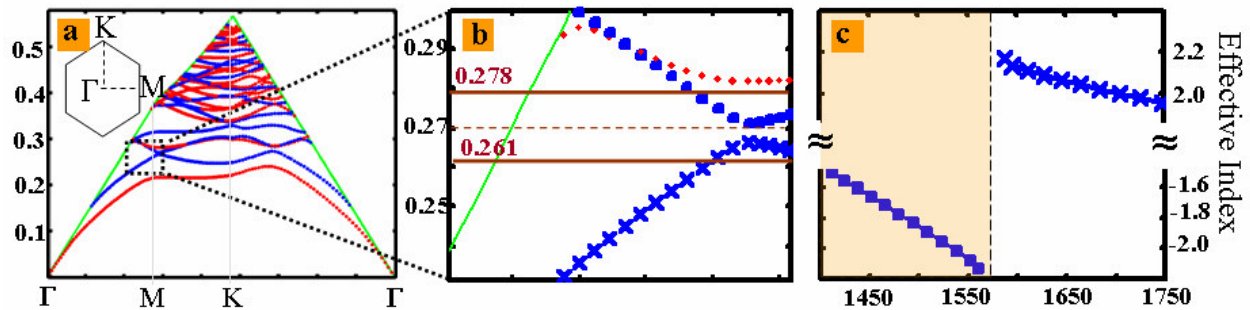


Figure S2 | Band diagram of the PhC, a, Band diagram of the PhC with the parameters given in Fig. 1. Inset: first Brillouin zone of the hexagonal PhC (for a schematic of the Brillouin zones, see the Supplementary Information, Fig. S1). The TM-like (TE-like) photonic bands are depicted in blue (red). The light cone is denoted by the green lines. **b**, A zoom-in of the spectral domain corresponding to experimental region of interest. Experiments were performed in the spectral region marked by the two horizontal lines (0.278-0.261 normalized frequency; 0.270 (dashed line) to 0.278 is negative index region). There is a complete TE-like band gap, and there are two TM-like bands. Lower frequency one band (marked with \times) has positive effective index of refraction, higher frequency band (marked with \blacksquare) has negative effective index of refraction. **c**, Calculated effective index of refraction of the PhC, corresponding to the two TM-like bands shown in Fig. S2b marked with the same symbols.

III. Device modification for phase measurements, and theoretical calculations for interferometer transmission

Figure S3 shows a schematic representation of a device with 2 superperiods and the integrated Mach Zehnder Interferometer is modified after introducing the third superperiod. The adiabatic region remains unchanged if L_1 is increased to $L_1 + \Lambda$ and L_2 is shortened by $\Lambda/2$, in both the input and output sides of the device. To keep the total length of the waveguide unchanged, the length L_3 is increased to $L_3 + \Lambda/2$. This procedure is used each time a superperiod is added to the structure. In addition, to be able to compare devices with different number of unit cells in the PhC layer, a common reference point is used for all devices that have the same d_2/d_1 ratio.

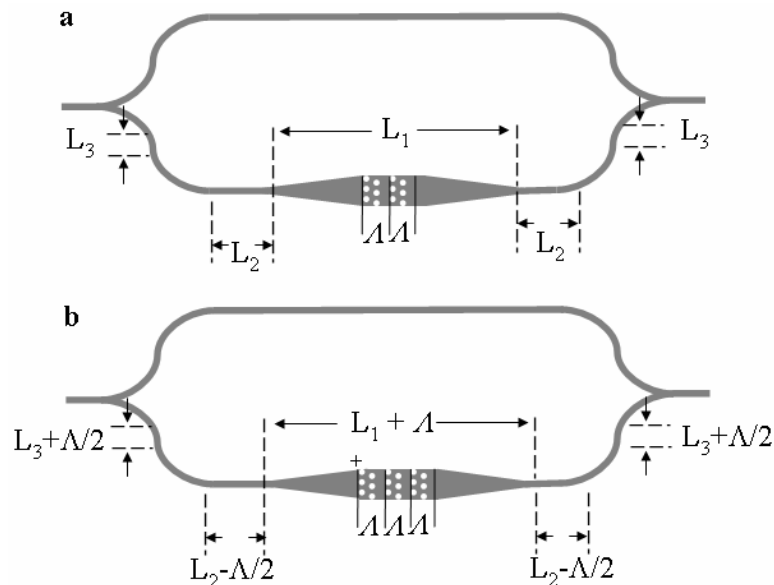


Figure S3| Schematic representation of the device modification induced by adding a superperiod. a, Integrated MZI of a device with 2 superperiods and a channel waveguide. **b,** Device modifications after the third superperiod is added. The length of the channel waveguide remains the same so as the effect of the additional superperiod is isolated.

In our implementation, the interferometer output intensity is given as:

$$I = I_1 + I_2 + 2\sqrt{I_1 I_2} \cos \phi \quad (\text{S1})$$

where ϕ is the phase difference (or imbalance) between the modes propagating in the two arms (denoted by subscript 1 and 2). Considering our implementation, the phase ϕ can be decomposed as:

$$\begin{aligned}\phi &= \phi_1 - \phi_2 = \frac{2\pi}{\lambda} \left[(n_{wg} L_{wg_1} + n_{slab_1} L_{slab_1} + n_{sl} L_{sl}) - n_{wg} L_{wg_2} \right] \\ &= \frac{2\pi}{\lambda} \left[n_{wg} (L_{wg_1} - L_{wg_2}) + n_{slab_1} L_{slab_1} \right] + \frac{2\pi}{\lambda} n_{sl} L_{sl}\end{aligned}\quad (S2)$$

where n_{wg} , n_{slab_1} , n_{sl} are the effective mode refractive indices of the channel waveguide, the adiabatic slab in arm 1, and the zero-index superlattice, respectively. L_i denotes the corresponding lengths.

We note that the difference between the physical path length of the channel waveguides on both arms is designed to be equal to the physical path length of the tapering slab. Thus we have:

$$\begin{aligned}\cos[\phi] &= \cos \left[\frac{2\pi}{\lambda} \left((-n_{wg} L_{slab_1} + n_{slab_1} L_{slab_1}) + n_{sl} L_{sl} \right) \right] \\ &= \cos \left[\frac{2\pi}{\lambda} \left((n_{slab_1} - n_{wg}) L_{slab_1} + n_{sl} L_{sl} \right) \right] \\ &= \cos[\phi_{slab_wg} + \phi_{sl}]\end{aligned}\quad (S3)$$

The mode indices n_{wg} , n_{slab_1} , n_{sl} have different frequency dispersion. We kept the phase (ϕ_{slab_wg}), arising from $\frac{2\pi}{\lambda} (n_{slab_1} - n_{wg}) L_{slab_1}$, constant between different devices in each set of measurements by simply ensuring that the physical lengths and widths of the slabs are the same for each nanofabricated device. The remaining phase variation therefore is generated only by the photonic crystal superlattice ($\phi_{sl} = \frac{2\pi}{\lambda} n_{sl} L_{sl}$). If n_{sl} is equal to zero, ϕ_{sl} is zero too, hence the total phase difference ϕ in the interferometer arises only from the ϕ_{slab_wg} component and is the same

for all the devices in each set. Therefore, the sinusoidal oscillations in the transmission and the free spectral range are determined only by ϕ_{slab_wg} .

IV. Experiments on tunability of the zero- \bar{n} region

In order to demonstrate the tunable character of the zero- \bar{n} bandgaps, we performed transmission experiments on four sets of binary superlattices, with each set having different superlattice ratios: $d_2/d_1=0.74$ (Fig. S4a), $d_2/d_1=0.76$ (Fig. S4b), $d_2/d_1=0.78$ (Fig. S4d), and $d_2/d_1=0.8$ (Fig. S4e). In all our experiments the negative index PhC has the same parameters as those given in the main text. Note that there is a slight ($\sim 5\%$) change in r/a , which results in a small shift ($<1\%$) in the spectrum. For example, Fig. 2c in the main text and Fig. S4d here correspond to the same design but there is about 10 nm ($\sim 0.6\%$) shift in the center of the zero- \bar{n} region. However, all the experimental data in this section corresponds to the same chip, therefore the invariance of the gap for the geometrical changes and its tunability can be clearly observed.

As described in the main text, each set of photonic superlattices consists of three devices of different period Λ , with the negative index PhC layer in the superlattice spanning 7, 9, and 11 unit cells along the z -axis, so that the thickness of this layer is $d_1 = 3.5\sqrt{3}a$ (2.564 μm), $d_1 = 4.5\sqrt{3}a$ (3.297 μm), and $d_1 = 5.5\sqrt{3}a$ (4.029 μm), respectively. The corresponding thickness of the PIM layer is determined by requiring that the average index is zero [$\bar{n} = (n_1 d_1 + n_2 d_2)/\Lambda = 0$], while keeping the ratio d_2/d_1 unchanged for all devices in each set (see Table S1). Here, n_1 and n_2 are the effective mode indices in the PhC and homogeneous (PIM) layers, respectively, at the corresponding wavelength.

Table S1 | Calculated parameters of the devices in the Fig. S4 (units in μm).

Fig. S4a			
# of unit cells	d_1	d_2	Λ
7	2.56	1.90	4.46
9	3.30	2.44	5.74
11	4.03	2.98	7.01

Fig. S4b			
# of unit cells	d_1	d_2	Λ
7	2.56	1.95	4.51
9	3.30	2.51	5.80
11	4.03	3.06	7.09

Fig. S4d			
# of unit cells	d_1	d_2	Λ
7	2.56	2.00	4.56
9	3.30	2.57	5.87
11	4.03	3.14	7.17

Fig. S4e			
# of unit cells	d_1	d_2	Λ
7	2.56	2.05	4.62
9	3.30	2.64	5.93
11	4.03	3.22	7.25

For the three devices in each set, we designed 7 SPs for the devices with 7 unit cells of PhC and 5 SPs for those with 9 and 11 unit cells of PhC (these designs ensure a sufficient signal-to-noise ratio for the transmission measurements). In these experiments we have tested both the existence of the zero- \bar{n} bandgap as well as its tunability. For the three devices belonging to each set, we observed the zero- \bar{n} bandgap at the same frequency whereas the spectral locations of the other bandgaps were observed to shift with the frequency – this confirms the zero- \bar{n} bandgap does not depend on the superperiod length Λ (the gap existence is dependent only on the condition of path-averaged zero index: $n_1 d_1 + n_2 d_2 = 0$) while the frequency of the regular 1D PhC Bragg bandgaps does depend on Λ . Our measurements show that the invariant, zero- \bar{n} , bandgap is located at 1525.5 ± 1 nm, 1535.2 ± 2 nm, 1546.3 ± 1.5 nm, and 1556.5 ± 2.5 nm,

respectively (averaged over the three devices in each set). The slight red-shift with increasing number of unit cells in each set is due to effects of edge termination between the PhC and the homogeneous slab.

Furthermore, when we tuned the ratio d_2/d_1 and repeated these same experiments we observed a redshift (see the values above) of the zero- \bar{n} mid-gap frequency as we increased the ratio d_2/d_1 . This result is explained by the fact that for the negative index band the refractive index of the 2D hexagonal PhC decreases with respect to the wavelength (see Fig. S2c) and therefore when the length of the PIM layer in the 1D binary superlattice increases (higher d_2/d_1), the wavelength at which the effective index cancels is red-shifted. The effective index of the PIM layer, n_2 , is calculated numerically and for the asymmetric TM slab waveguide mode corresponds to, for example, 2.671 at 1550 nm. By using these n_1 (Fig. S2c) and n_2 values, we determined the average refractive index for the different d_2/d_1 ratios as summarized in Fig. S4f. A distinctive red-shift in the zero- \bar{n} gap location is observed with increasing d_2/d_1 ratios from the numerically modeling, demonstrating good agreement ($\sim 0.5\%$ difference) with the experimental measurements (Fig. S4a, 4b, 4d, and 4e). Furthermore, Fig. S4c shows how the spectral features of the zero- \bar{n} bandgap changes with increasing the number of superperiods. We note that this is the first rigorous and complete experimental confirmation of invariant and tunable character of zero- \bar{n} bandgaps in photonic superlattices containing negative index PhCs.

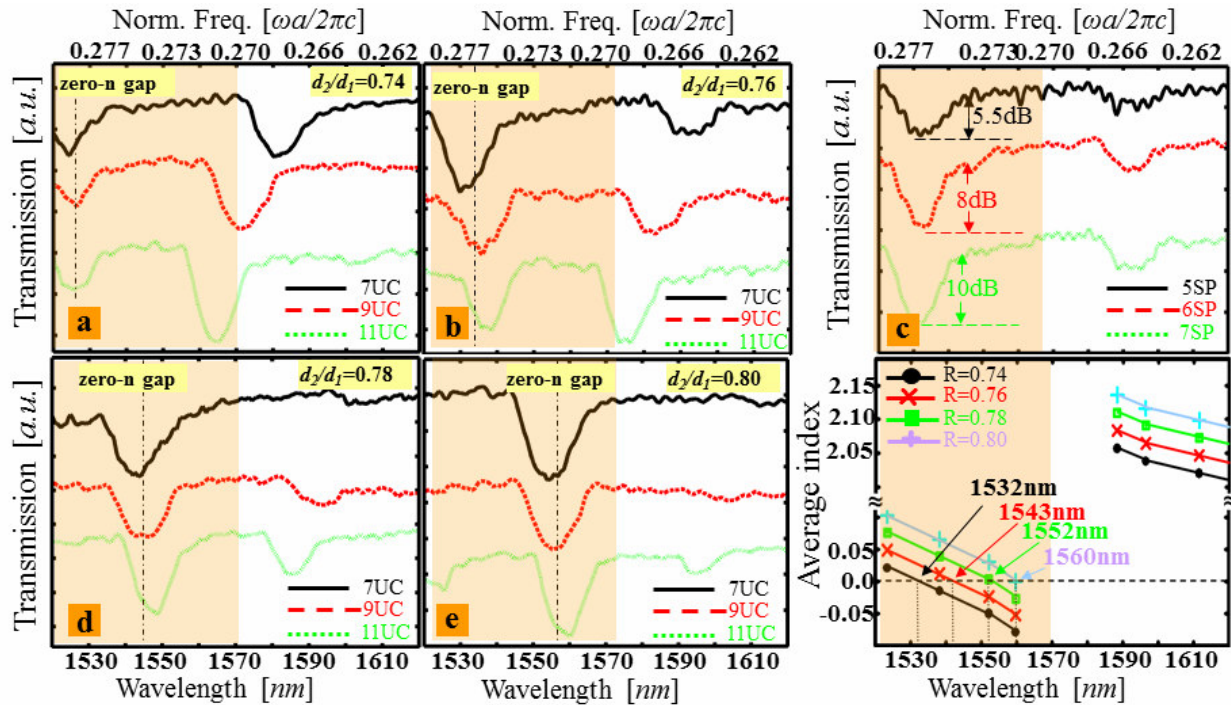


Figure S4 | Experimental verification of period-invariance and tunability of zero- \bar{n} bandgaps. **a**, Experimental verification of the zero- \bar{n} bandgap in superlattices with varying period (A). The ratio $d_2/d_1 = 0.74$ and $A = 4.46 \mu\text{m}$ for black (solid), $5.74 \mu\text{m}$ for red (dashed), and $7.01 \mu\text{m}$ for green (dotted) curves (a.u. arbitrary units). **b**, Same as in **a**, but for $d_2/d_1 = 0.76$. $A = 4.51 \mu\text{m}$ for black (solid), $5.80 \mu\text{m}$ for red (dashed), and $7.09 \mu\text{m}$ for green (dotted) curves. **c**, Transmission spectra for superlattices with $d_2/d_1 = 0.76$, containing 5, 6, and 7 superperiods (SPs). Each PhC layer contains 7 unit cells ($d_1 = 2.564 \mu\text{m}$, $A = 4.51 \mu\text{m}$). **d**, Same as in **a**, but for $d_2/d_1 = 0.78$. $A = 4.56 \mu\text{m}$ for black (solid), $5.87 \mu\text{m}$ for red (dashed), and $7.17 \mu\text{m}$ for green (dotted) curves. **e**, Same as in **a**, but for $d_2/d_1 = 0.80$. $A = 4.62 \mu\text{m}$ for black (solid), $5.93 \mu\text{m}$ for red (dashed), and $7.25 \mu\text{m}$ for green (dotted) curves. **f**, Calculated effective index of refraction for the superlattices with the ratios in **a**, **b**, **d**, and **e**. The wavelengths at which the average index of refraction cancels agree very well with the measured values.

V. Near-field scanning optical microscopy and high-resolution imaging measurements

We further used near-field scanning optical microscopy (NSOM) to examine the zero- \bar{n} transmission in the near-field, as illustrated in Fig. S5. Our NSOM is an aperture-type instrument, where the fiber is produced in National Chiao Tung University in Taiwan by using of thermal pulling method. A metal coating is used to create the aperture. The NSOM fiber was then attached to a tuning fork sensor produced by Veeco Instruments. The detection is performed with a New Focus 2153 InGaAs femtowatt photoreceiver with lock-in amplification. The NSOM instrument is a modified Veeco Aurora-3.

Coupling light into the zero- \bar{n} superlattices is achieved by UV-curing adhesive bonding of a tapered lens fiber to the silicon input waveguide. The input fiber was stably UV-epoxy bonded to the devices selected for the measurements. We observed the light propagation through the sample by NSOM and used a widely tunable laser with controlled polarization to vary the input wavelength. From the near-field images of the superlattices (9 unit cells in PhC layer and $d_2/d_1 \sim 0.76$), it can be seen that the light propagation in the superlattices is characterized by low transmission inside the zero- \bar{n} gap (Fig. S5a, $\lambda=1535$ nm), and high transmission outside the zero- \bar{n} gap (Fig. S5b, $\lambda=1560$ nm).

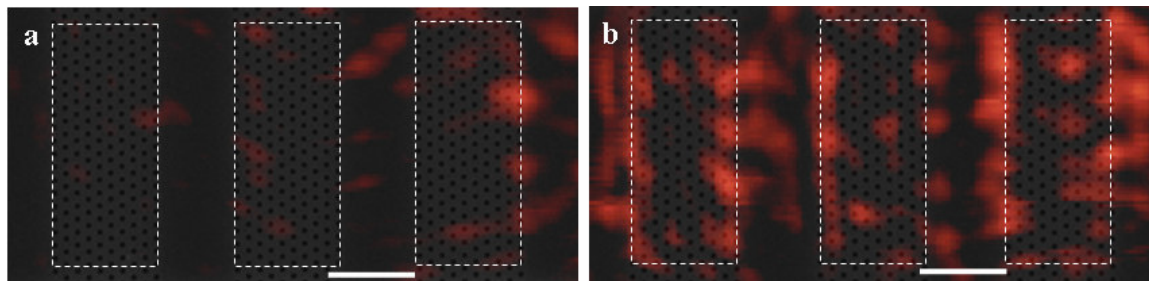


Figure S5| Near-field scanning optical microscopy of zero- \bar{n} superlattices. a, Near-field image of a zero- \bar{n} device that has 9 unit cells in each PhC layer at $\lambda=1535$ nm (in the center of

the gap). **b**, Same as in **a** at $\lambda=1560$ nm (in the high transmission). Scattering occurs at the edge of the PhC/PIM interfaces and is an indicative of transmission. Scale bar: $2.5\ \mu\text{m}$.

In addition, we performed high spatial resolution imaging of the radiated input-output ports for the devices that have been used for the experiment presented in Fig.3c. Results are illustrated in the Fig S6 as follow: In the case of the reference arm (**i-iii**), we see light transmission for all three wavelengths, which corroborates the characteristics of the transmission spectrum in Fig. 3c. For the device arm (**iv-vi**) there is transmission for 1600 nm and 1530 nm but not for 1570 nm. This agrees with the transmission spectra in Fig. 3c. Note that although there is similar transmission for both arms at 1530 and 1600 nm, the interference output has 14dB difference.

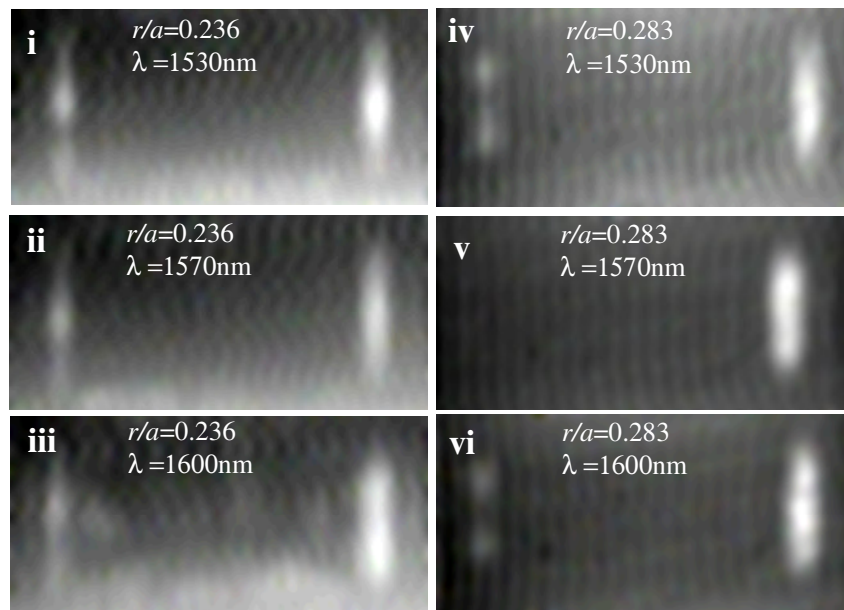


Figure S6| Infrared images pertaining to the experiments corresponding to Fig3c. i-iii is taken from the reference arm containing a PhC structure with $r/a=0.236$ and **iv-vi** is taken from the device arm where the ratio $r/a=0.283$. In all the images the input beam is impinging onto the structure from the right, which means that light scattering at the left facet of the device indicates light transmission.

VI. Computational study of the influence of disorder on the properties of zero- \bar{n} superlattices.

In addition to the model for structural disorder of the photonic superlattice discussed in the paper, we have also considered two other disorder models in which either the radius of each hole in the PhC sections or the position of the holes is randomly perturbed. More exactly, the radius of the holes is set in the domain $(r-\Delta r/2, r+\Delta r/2)$, according to a uniform random distribution whereas in the second case the location of the holes is randomly perturbed by Δl . In these models, the degree of structural disorder is characterized by a disorder parameter defined as $\sigma=\Delta r/r$ and $\sigma=\Delta l/a$, respectively. The main results of our computational investigations are summarized in Fig. S7. Thus, it can be seen that in the case of random perturbation of the radius of the holes the transmission spectra in the superlattice are only slightly affected, even if the disorder parameter is as large as $\sigma=10\%$. As observed, the main effect consists of a small decrease of the zero- \bar{n} superlattice transmission with increasing values of the disorder parameter σ . It is seen, however, that structural disorder induced by randomly changing the location of the holes has a much larger effect on the transmission spectra. We note though that a value of $\sigma=10\%$ corresponds to variations of tens of nanometers of the location of the holes, variations which are much larger than those measured in our fabricated devices.

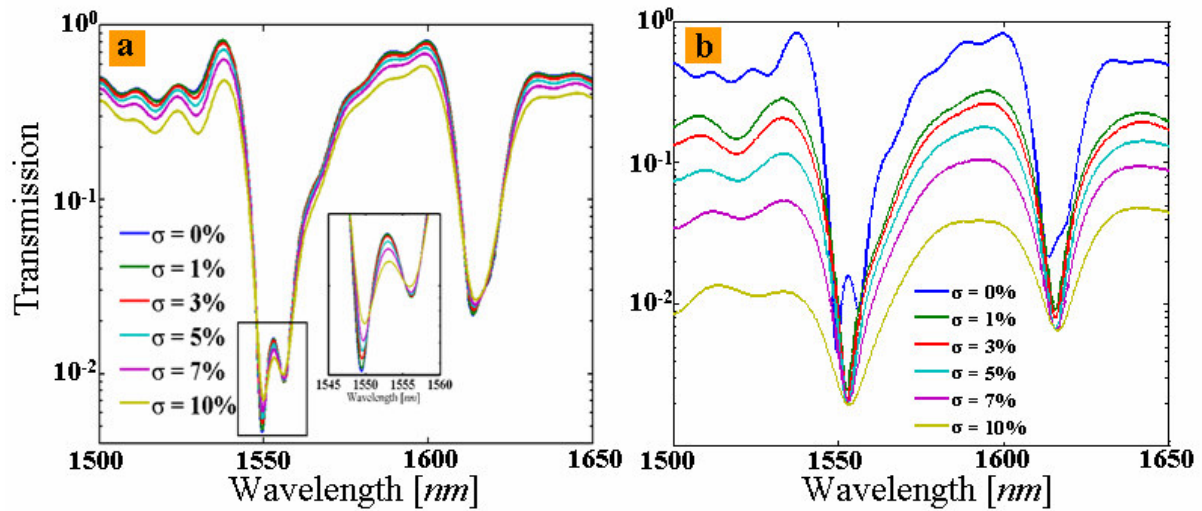


Figure S7 | Transmission spectra calculated for different values of the disorder parameter σ . The inset shows the expanded transmission spectra. **a**, The structural disorder is introduced by randomly changing the radius of the holes in the PhC sections of the superlattice. **b**, The structural disorder is generated by randomly perturbing the location of the holes.

suggests that the density of Cooper pairs remains unchanged in the CuO_2 layers, which may allow the realization of almost decoupled 2D stacks with a Kosterlitz–Thouless superconducting transition. Interlayer coupling would simply allow 3D superconductivity to develop, yielding a larger value of the 3D ordering temperature. An alternative scenario suggests that the condensed state does not survive in the absence of the Josephson coupling⁷. This work could

have potential applications in signal transmission and light switching, once the gating field can be controlled to allow the phase differences to reach multiples of π and $\pi/2$. □

Marc Gabay is in the Laboratoire de Physique des Solides, Bat 510, Université Paris-Sud 11, 91405 Orsay, Cedex, France. Jean-Marc Triscone is at the Département de Physique de la Matière Condensée, University of Geneva, 24 quai E.-Ansermet, 1211 Geneva 4, Switzerland.

e-mail: marc.gabay@u-psud.fr;
jean-marc.triscone@unige.ch

References

1. Dienst, A. *et al.* *Nature Photon.* **5**, 485–488 (2011).
2. Ahn, C. H., Triscone, J.-M. & Mannhart, J. *Nature* **424**, 1015–1018 (2003).
3. Triscone, J.-M. & Gabay, M. *100 Years of Superconductivity* (eds Rogalla, H. & Kes, P.) Ch. 3.5, 197–206 (CRC, 2011).
4. Bollinger, A. T. *et al.* *Nature* **472**, 458–460 (2011).
5. Suzuki, M. & Hikita, M. *Phys. Rev. B* **44**, 249–261 (1991).
6. Lawrence, W. E. & Doniach, S. in *Proc. 12th Int. Conf. Low Temperature Physics* (ed. Kanda, E.) 361–362 (Keigaku, 1971).
7. Anderson, P. W. *Science* **279**, 1196–1198 (1998).

FUNDAMENTAL OPTICAL PHYSICS

The quest for zero refractive index

A superlattice comprising alternating layers of negative-refractive-index photonic crystals and positive-refractive-index dielectric media has been shown to exhibit an effective refractive index of zero. Experiments show that light passing through such a material experiences no phase shift.

Jörg Schilling

During the early years of research into metamaterials, many scientists strived to fabricate structures with negative refractive index (n). Recently, some interest has shifted towards the realization of materials that exhibit zero or near-zero refractive index. A refractive index of zero implies that light enters a state of quasi-infinite phase velocity and infinite wavelength. It also means that every point within the metamaterial experiences a quasi-uniform phase of the light wave present, as though all the dipoles inside the metamaterial are oscillating in unison. Thus, the shape of the wavefronts leaving the metamaterial depends solely on the shape of the exit surfaces of the metamaterial, which provides high flexibility in the design of phase patterns¹. A simple planar slab of a zero- n material could, in principle, function as a highly selective angular filter that allows the transmission of plane waves only at normal incidence. By applying convex or concave surfaces, the outgoing wavefronts could be either divergent or focusing.

The uniform phase distribution of light within such a material may also have far-reaching consequences for light emission. Placing an emitter inside a zero- n material creates a radiation field with spatially uniform phase inside the material, which produces a highly directional and collimated outgoing beam at an extended planar surface². Because the phase is spatially independent, the exact position of the radiation source inside the zero- n

material seems to be irrelevant and the formation of a single collimated beam from many spatially distributed point sources should be possible.

Researchers have attempted to realize a material with zero refractive index (or zero permittivity, ϵ) through several different strategies. One suggestion was to use metallic metamaterial structures such as stacked frequency-selective surfaces. Alternative approaches include the use of microwave waveguides close to the mode cut-off³ and the combination of negative- and positive-index materials^{4,5}.

Serdar Kocaman and colleagues, reporting in this issue of *Nature Photonics*⁶, have now constructed a one-dimensional (1D) periodic superlattice from alternating strips of unpatterned regions of positive-refractive-index dielectric media and 2D negative-refractive-index photonic crystals. Using phase-sensitive interferometric measurements, they have demonstrated that light of a specific frequency propagating through such a superlattice experiences no change of phase. Thus, from a macroscopic view point, the superlattice exhibits an effective refractive index (\bar{n}) of zero.

The layered structure is formed in slab waveguides that have been fabricated on silicon-on-insulator substrates by structuring the thin top silicon layer. Each superlattice period, Λ , consists of two sections with widths of d_1 and d_2 (Fig. 1). The first section (width d_1) contains a 2D photonic crystal with a hexagonal pore

array fabricated by electron beam or deep-ultraviolet lithography. The second section (width d_2) is an unpatterned section of the waveguide slab. The period and pore radius of the photonic crystal section were chosen in such a way that light with a wavelength of $\lambda_0 = 1,552$ nm couples to a mode of the second photonic band of transverse-magnetic-like polarization. Because the second photonic band has a negative slope within the first Brillouin zone, the group velocity appears negative, meaning that the directions of phase propagation and energy propagation are counter-parallel. Kocaman *et al.* describe this propagation by a negative refractive index n_1 whose absolute value is derived from the band structure within the first Brillouin zone.

The phase of a wave travelling through the photonic crystal section changes by $\Delta\phi_1 = n_1 d_1 k_0$, where k_0 is the free-space wavenumber. Because the refractive index n_1 is negative, the phase of the wave actually evolves backwards and accumulates a negative relative phase in the photonic crystal layer. However, when the wave propagates through the subsequent unpatterned section with positive refractive index n_2 , its phase changes by $\Delta\phi_2 = n_2 d_2 k_0$. Because the refractive index of this layer is positive, the phase evolves forwards and the negative phase accumulated in the photonic crystal layer ‘unwinds’. If the ratio between the two superlattice layer thicknesses, d_1/d_2 , is adjusted to give $\Delta\phi_1 = -\Delta\phi_2$, the net phase change of the wave ($\Delta\phi_1 + \Delta\phi_2$) after traversing the whole superlattice

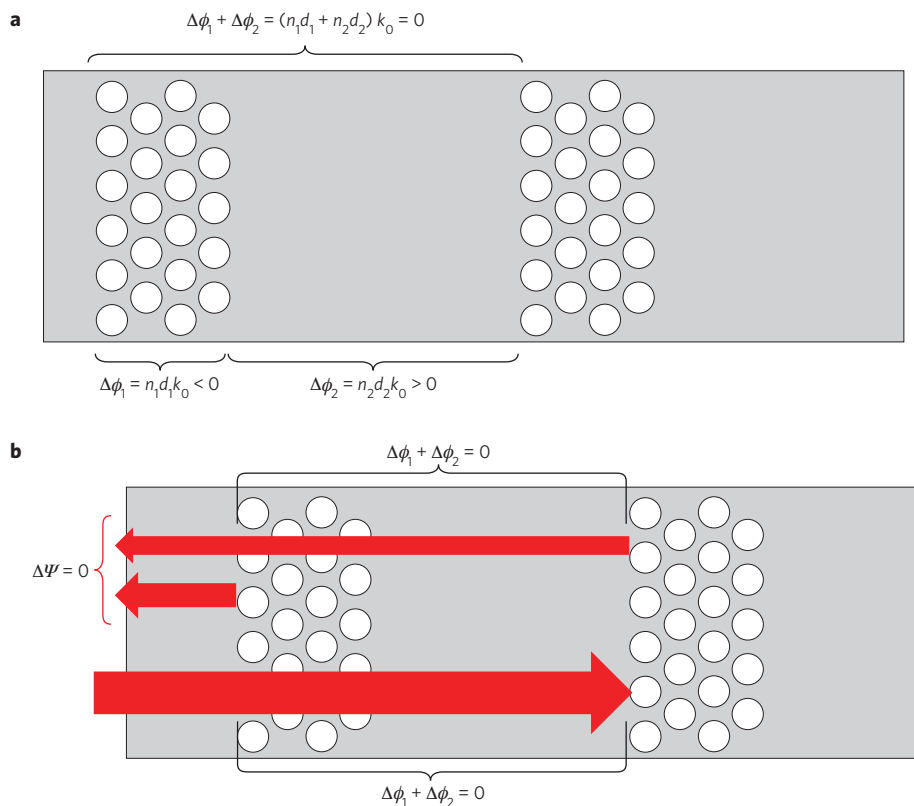


Figure 1 | Phase delays in a zero- \bar{n} superlattice. **a**, A superlattice with an effective refractive index of zero can be realized by combining negative-refractive-index photonic crystal sections (width d_1) and positive-refractive-index unpatterned waveguide sections (width d_2). Negative and positive phase changes ($\Delta\phi_1$ and $\Delta\phi_2$) cancel out at the design wavelength, leading to an overall phase change of zero ($\Delta\phi_1 + \Delta\phi_2 = 0$) over the whole superlattice period. **b**, Development of the zero- n bandgap. Because the average refractive index over each superlattice period is zero, the optical path length and the accumulated phase $\Delta\Psi$ for all the Bragg-reflected waves is also zero. The interference of all the Bragg-reflected waves is therefore always constructive and independent of the length of the superlattice period, which results in a zero- n bandgap.

period Λ is zero; that is, the effective index of the superlattice is $\bar{n} = 0$. However, this condition can only be fulfilled for a single wavelength because n_i is highly dispersive and a near-zero \bar{n} can only be obtained in a narrow spectral range. To experimentally demonstrate a zero- n material, Kocaman *et al.* employed two strategies.

First, the researchers observed the formation of the zero- n bandgap in transmission measurements. Bragg reflection generally leads to the formation of bandgaps in photonic crystals. For the case of a zero effective index in the superlattice, the phase difference between the wavelets of light reflected at the first superlattice period and those reflected at subsequent periods is zero. This corresponds to the zeroth order of the Bragg condition. This zero- n bandgap was observed in the transmission spectra as a dip between wavelengths of 1,550 nm and 1,565 nm. To demonstrate that the observed dips are indeed due to the

expected zero- n bandgaps, Kocaman *et al.* prepared several superlattices with different periods Λ , but kept the ratio d_1/d_2 constant. The observed spectral independence of the bandgap position from the period of the superlattice gives a clear indication that the observed bandgap is indeed the expected zero- n bandgap.

Second, Kocaman *et al.* used an interferometric technique to monitor the relative phase change of the wave travelling through the superlattice. The superlattice structure was included in one arm of a Mach–Zehnder interferometer, whose second arm represented a reference, unstructured waveguide. Interference fringes appeared in the transmission spectra after the light from both arms was rejoined, owing to the inherent difference in optical path length. The researchers observed that adding further superlattice periods (and thus extending the geometric path for light travelling through the superlattice arm) does not

change the position or spectral period of the interference fringes within the spectral range of the zero- n bandgap. They also changed the length of the superlattice period but again did not observe an impact on the position or period of the interference fringes within the zero- n bandgap. Changing the number or length of the superlattice periods therefore did not influence the accumulated phase of the light propagating through the superlattice, even though the geometric path length in the superlattice was being varied. This is only possible if the superlattice periods do not contribute to the phase accumulation because the optical path length within the superlattice is zero, which corresponds to $\bar{n} = 0$.

Through these phase-sensitive measurements, Kocaman *et al.* demonstrated that a superlattice consisting of alternating 2D photonic crystal and unpatterned waveguide sections can exhibit an effective refractive index of zero while also providing zero relative phase delay. Furthermore, they showed that the average refractive index \bar{n} can be controlled by adjusting the relative thicknesses of the superlattice period (d_1 and d_2). Tuning the ratio d_1/d_2 shifts the spectral position of the zero- n bandgap and thus achieves complete phase compensation for another wavelength. It is therefore possible to fulfil the zero- n condition at nearly any desired wavelength, which provides enhanced flexibility in system design.

Using dielectric photonic crystals to provide the negative refractive index avoids Ohmic losses, which are intrinsic to metallic metamaterials. This is particularly important for structures operating at visible and near-infrared frequencies because their comparatively deeper penetration into metals causes significant losses. Ohmic dissipation, which is related to the conversion of electromagnetic energy to phonons (heat) through the damping of free electrons in the metal, is not present in a dielectric material. However, even photonic crystal superlattices made from nearly lossless dielectric materials suffer from systematic transmission losses due to scattering and out-of-plane diffraction. The period of the superlattice is several micrometres in length, which allows it to function as a grating coupler that can diffract light out of the thin silicon slab, thereby lowering transmission levels in the waveguide. This fact has already been used to observe light propagation through a similar superlattice structure⁵. Furthermore, the zero- n bandgap exists at the design wavelength, where the zero- n condition is exactly

fulfilled. This causes considerable back-reflection, which reduces transmission levels, especially when the number of superlattice periods is increased. These effects therefore limit the size of structure that can practically be employed before the intensity of the transmitted light becomes too low.

It is useful to compare the negative refractive indices found in metal metamaterials and dielectric photonic crystals, given the key role played by the negative refractive index section of the superlattice in the work of Kocaman *et al.* In metamaterials, a negative refractive index is usually achieved by combining two different kinds of resonators (wires and split rings) driven at a frequency slightly above their resonance. Each resonator therefore radiates more than 90° out of phase with their individual excitation, leading to both negative permeability and negative permittivity — ‘backwards’ waves. Although such individual resonators do not exist in photonic crystals, the generation of backwards-evolving waves is achieved by Bragg reflection due to the periodic variation of the refractive index. Whereas metamaterials avoid diffraction by using subwavelength-sized structures, photonic crystals use diffraction

as the source for negative-refractive-index behaviour.

It should be noted that the description of wave propagation through a periodic structure with a single negative refractive index could be misinterpreted if care is not taken. A wave in a periodic structure travels as a Bloch mode, which is represented by a sum of many plane waves with different directions of propagation and spatial periods (both defined by their wave vector). For example, the wave vector of the j th plane wave is defined by the condition $\mathbf{K} + \mathbf{G}_j$, where \mathbf{K} is the wave vector in the first Brillouin zone and \mathbf{G}_j is any reciprocal lattice vector (j being an integer). This multitude of wave vectors makes it non-trivial to define a single refractive index. The absolute phase change of each plane wave component is different along the considered propagation direction. Over an integer of N periods of propagation in the photonic crystal, the phase change is $\Delta\varphi_{1,j} = n_1 d_1 k_0 + Nj2\pi$. However, the additional term — an integer multiple of 2π — is irrelevant when evaluating interferometric results; only the negative relative phase change $n_1 d_1 k_0$ has an impact. This relative phase change matches the negative absolute phase change of the plane wave component of the first

Brillouin zone considered by Kocaman *et al.*, and therefore justifies the description of wave propagation through the photonic crystal slabs by a negative refractive index for the described situation.

The superlattice approach is currently restricted to 1D propagation. However, 2D wave propagation is desirable to realize sophisticated phase-shaping schemes. In addition, a zero- n material with curved entrance and exit surfaces might be of interest for new optical elements that take advantage of the zero accumulated phase or uniform phase within the structures. Whether or not this can be achieved using photonic crystal superlattices remains to be seen. \square

Jörg Schilling is at the ZIK SiLi-nano, Martin Luther University of Halle-Wittenberg, Karl-Freiherr-von-Fritsch Str. 3, 06120 Halle, Germany.
e-mail: joerg.schilling@physik.uni-halle.de

References

1. Alu, A., Silveirinha, M. G., Salandrino, A. & Engheta, N. *Phys. Rev. B* **75**, 155410 (2007).
2. Enoch, S., Tayeb, G., Sabouroux, P., Guerin, N. & Vincent, P. *Phys. Rev. Lett.* **89**, 213902 (2002).
3. Edwards, B., Alu, A., Young, M. E., Silveirinha, M. & Engheta, N. *Phys. Rev. Lett.* **100**, 033903 (2008).
4. Li, J., Zhou, L., Chan, C. T. & Sheng, P. *Phys. Rev. Lett.* **90**, 083901 (2003).
5. Mocella, V. *et al.* *Phys. Rev. Lett.* **102**, 133902 (2009).
6. Kocaman, S. *et al.* *Nature Photon.* **5**, 499–505 (2011).

ATOM OPTICS

Marriage of atoms and plasmons

The interaction between atoms in a Bose–Einstein condensate and plasmon-enhanced fields is a step towards the goal of realizing hybrid atom–polariton systems for tasks in quantum information processing.

James P. Shaffer

Surface polaritons and atoms can both be quantum objects, yet their unique characteristics make them suitable for different tasks. Atoms can be isolated from their environment and manipulated precisely with lasers, which makes them good candidates for storing information and building single-photon sources, traceable sensors and quantum gates. Surface polaritons, in contrast, are capable of interfacing with solid-state devices and being moved around on a surface using micro- and nanostructures. They are therefore an attractive means of transporting quantum information from one point to another on a microscopic chip, perhaps between different clouds of trapped atoms. The individual advantages of atoms

and polaritons can be combined to allow the realization of sophisticated circuits.

One important future goal is to develop efficient hybrid quantum devices in which individual excitations can be transferred between atoms and polaritons on demand, thus allowing both systems to be used to their maximum advantage. Information-processing circuits that exploit both atoms and surface polaritons and operate using the principles of quantum entanglement are an important example of what might be achievable in the future.

Although such hybrid atom–polariton systems are still a long way from fruition, the work of Stehle *et al.*¹ demonstrates an important preliminary step towards their realization. Writing in this issue

of *Nature Photonics*, Stehle *et al.* report the interaction of a Bose–Einstein condensate (an ultracold collection of atoms that share the same quantum state and thus behave as a single entity) with small customized surface potentials. The potentials were created from the plasmonic electromagnetic fields formed by tailored metallic microstructures on the surface of a prism. It is hoped that such potentials could eventually be used to guide atoms around circuits.

Surface plasmons are a type of surface polariton that result from the coupling between an electromagnetic field and collective oscillations of the conduction electrons in a metal. They can be created using light and propagate along the